



## Technical Data

**HTP 180**  
**HTP 280**

### HANDLING PROPERTIES

Property	Standard	Units	72°F (22°C)
150g Pot Life	ASTM D2471	minutes	180
500g Pot Life	ASTM D2471	minutes	120
Viscosity Mixed	ASTM D2196	cP	600
Viscosity (resin)	ASTM D2196	cP	2,500
Viscosity (hardener)	ASTM D2196	cP	35


### MIX RATIO

Method	Resin:Hardener	Resin:Hardener
Weight	3.70:1	100:27.0
Weight Range	3.80:1 - 3.50:1	100:26.3 - 100:28.5
Volume	3.00:1	100:33.3
Volume Range	3.08:1 - 2.84:1	100:32.4 - 100:35.2

### DENSITY

State	Units	72°F (22°C)
Cured	lb/gal (g/cc)	9.60 (1.15)
Resin	lb/gal (g/cc)	9.69 (1.16)
Hardener	lb/gal (g/cc)	7.85 (0.94)

### VISCOSITY VS TEMPERATURE

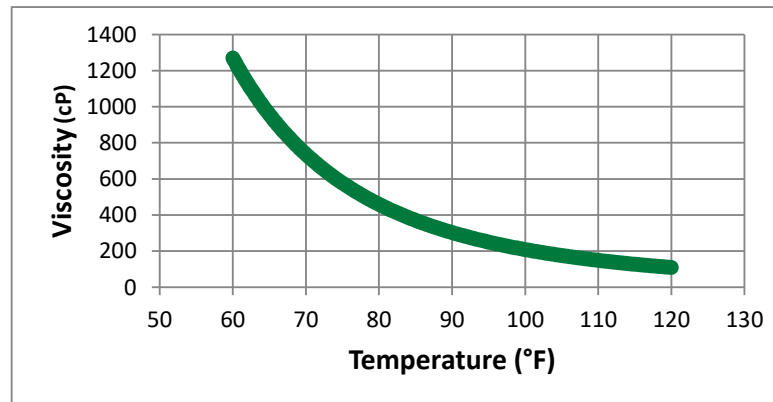

Test specimens were neat epoxy (without fiber reinforcement).  
Typical values, not to be construed as specification.

EPOXIES for  
Laminating  
Infusion  
Tooling  
Assembly

## HIGH-TEMP INFUSION EPOXY COMBINED FEATURES

**High-temperature, high-performance** epoxy formulation for synthetic composite part and tooling manufacture.

**T<sub>g</sub> as high as 300°F (149°C)** with proper post cure. Provides excellent temperature stability and great part cosmetics.

**Slow cure speed** hardener provides 5 to 6 hours of working time at 72°F (22°C). A typical laminate will gel in 10 to 12 hours at room temperature.

**This combination** is specifically formulated for resin infusion and VARTM processes. Not for use in open mold applications.

**Elevated temperature cure is required.** Parts can be pulled after 24-48 hours at room temperature or sooner after a mild initial cure of 90-110°F (32-43°C). See chart for post cure information.

Gougeon Brothers, Inc.  
P.O. Box 908  
Bay City, MI 48707  
prosetepoxy.com  
888-377-6738

ISO9001:2015 Certified

Rev 5 / April 2024

©2024 Gougeon Brothers, Inc.

To view more PRO-SET products, give us a visit at  
[fiberglasssupply.com](http://fiberglasssupply.com)!



# HIGH-TEMP INFUSION EPOXY


## MECHANICAL PROPERTIES

Property	Standard	Units	RT + 140°F (60°C) x 2hr + 225°F (107°C) x 12hr		RT + 140°F (60°C) x 2hr + 275°F (135°C) x 12hr	
Hardness	ASTM D2240	Type D	87		94	
Compression Yield	ASTM D695	psi (MPa)	15,300 (105)		15,300 (105)	
Tensile Strength	ASTM D638	psi (MPa)	10100	(70)	10800	(74)
Tensile Modulus	ASTM D638	psi (GPa)	407000	(2.81)	434000	(2.99)
Tensile Elongation	ASTM D638	%	3.9		5.5	
Flexural Strength	ASTM D790	psi (MPa)	15600	(108)	17800	(123)
Flexural Modulus	ASTM D790	psi (GPa)	439000	(3.03)	414000	(2.85)
Coefficient of Thermal Expansion	ASTM E831	in/(in*°F)(µm/(m*°C))	-	@ -22°F-86°F (-30°C-30°C)	2.98E-05 (53.57)	@ -22°F-86°F(-30°C-30°C)
			-	@ 86°F-248°F (30°C-120°C)	4.43E-05 (79.66)	@ 86°F-248°F(30°C-120°C)

## THERMAL PROPERTIES

Property	Standard	Units	RT + 140°F (60°C) x 2hr + 225°F (107°C) x 12hr		RT + 140°F (60°C) x 2hr + 275°F (135°C) x 12hr	
Tg DMA Peak Tan Delta	ASTM E1640 <sup>1</sup>	°F (°C)	281 (138)		320 (160)	
Tg DMA Onset Storage Modulus	ASTM E1640 <sup>1</sup>	°F (°C)	304 (151)		304 (151)	
Tg DSC Onset-1st Heat	ASTM E1640 <sup>1</sup>	°F (°C)	235 (113)		304 (151)	
Heat Deflection Temperature	ASTM E1356	°F (°C)	235 (113)		304 (151)	

## POST CURE SCHEDULE

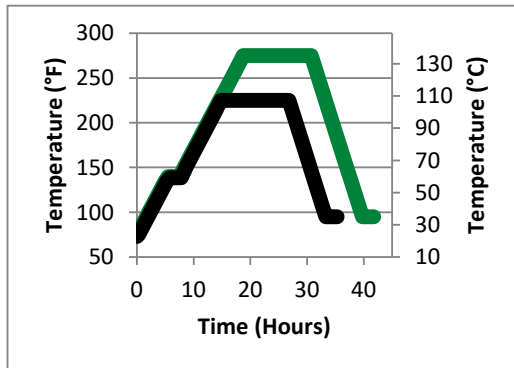

Post cure with ramp rates no greater than 12°F/hr, to achieve maximum properties. For larger parts, additional dwells may be required.

<sup>1</sup> 1 Hz, 3°C per minute.

<sup>2</sup> Store PRO-SET® Epoxy resins and hardeners at room temperature in sealed containers until shortly before use. As with many high-performance epoxy resins, repeated exposure to low temperatures during storage may cause the resin to crystallize. If this occurs, warm the resin to 125°F and stir to dissolve crystals. Hardeners may form carbamation when exposed to CO<sub>2</sub> and moisture in the atmosphere for extended periods of time. Prevent carbamation by protecting hardeners from exposure until immediately prior to processing.



<sup>2</sup>



QC Tinting Available